

Innovative, Environment-Friendly  
Inorganic, Non-combustible, Asbestos-free


Calcium silicate thermal insulation material  
ASTM C 533 Type I product

# DAIPALITE-Ei<sup>A</sup>

DAIPALITE-Ei<sup>A</sup> is a calcium silicate thermal insulation material which has water-repellent and chemical corrosion inhibition performance, and is used in various industrial facilities such as oil refinery plant, power plants, petrochemical plants, and others.

## Special effects of DAIPALITE-Ei<sup>A</sup>

DAIPALITE-Ei<sup>A</sup> is surface-treated with a special corrosion inhibitor containing soluble components ( $\text{Na}^+$ ,  $\text{SiO}_3^{2-}$ ). When the components are dissolved in water, the pH of the solution is more than 10, and a passive film is formed on the pipe surface, preventing iron corrosion.

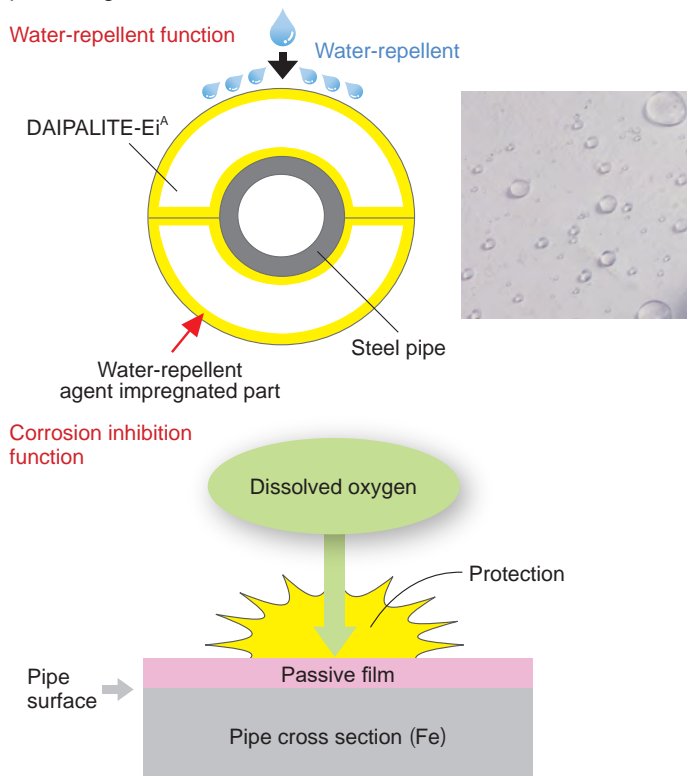


## Secular change of piping covered with thermal insulation material \*

\* The covered material is our water-repellent product, calcium silicate thermal insulation material made in Japan. DAIPALITE-Ei<sup>A</sup> has similar performance.



Crude oil piping at a thermal power plant (7 years) : The piping was covered with our water-repellent products. The small white circle on the pipe is due to the hole which was opened accidentally after the inspection. There is evidence that water has flowed for several years. The piping was not corroded.

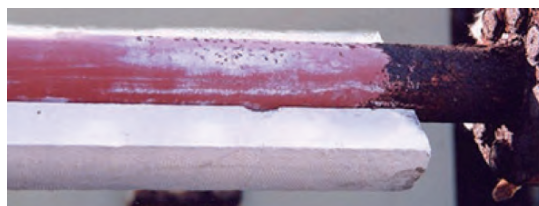

Steam (12K) piping at a steel plant (14years) : The left side was almost uncorroded where it was covered with our water-repellent products. On the right side, the corrosion was considerably progressing in the area covered with mineral fiber thermal insulation material.

## Standard physical properties of DAIPALITE-Ei<sup>A</sup> (reference values)

| Apparent Density     | Flexural Strength   | Compressive Strength  | Heating Linear Shrinkage | Maximum Service Temperature | Recommended service temperature range           | Thermal conductivity $\lambda$ [ $\text{W}/(\text{m} \cdot \text{K})$ ] , Temperature $\theta$ [ $^{\circ}\text{C}$ ]   |
|----------------------|---|---|--------------------------|-----------------------------|---|---|
| 170kg/m <sup>3</sup> | $\geq 344\text{kPa}$<br>( $\geq 34.4\text{N}/\text{cm}^2$ ) | $\geq 688\text{kPa}$<br>( $\geq 68.8\text{N}/\text{cm}^2$ ) | 2.0% max.                | 1000 $^{\circ}\text{C}$     | Ordinary temperature to 1000 $^{\circ}\text{C}$ | Pipe cover<br>$\lambda = 0.0489 + 7.885 \times 10^{-5} \cdot \theta + 2.032 \times 10^{-10} \cdot \theta^3$<br>Board<br>$\lambda = 0.0516 + 7.240 \times 10^{-5} \cdot \theta + 1.884 \times 10^{-10} \cdot \theta^3$ |


## Environment-friendly production process (original manufacturing method in Vietnam plant)

JIC is the first and the only one that succeeded in inventing the production process using rice husk. Rice husk is used as energies for reaction of raw materials and drying formed products. The rice husk ash is used for as a raw material instead of Silica rock. This unique process is certificated as an environment-conscious business by Viet Nam Government.



DAIPALITE-E series (Thermal Insulation Material Using Biomass) is registered to Sustainable Technology Promotion Platform (STePP) of United Nations Industrial Development Organization (UNIDO) Investment and Technology Promotion Office, Tokyo (ITPO Tokyo)

## Manufacturing process diagram

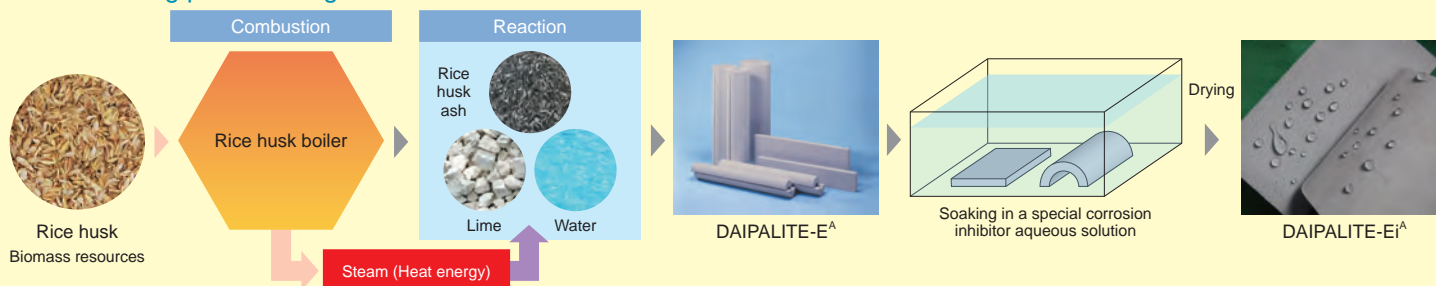


Innovative, Environment-Friendly  
Inorganic, Non-combustible, Asbestos-free

Calcium silicate thermal insulation material  
ASTM C 533 Type I product

# DAIPALITE-Ei<sup>A</sup>

## Water-repellent performance

In order to measure water-repellent and water absorption, the thermal insulation material was sprinkled for 60 minutes. The results are as follows. (by a test method similar to the JIS A 9510, measured in November 2020)

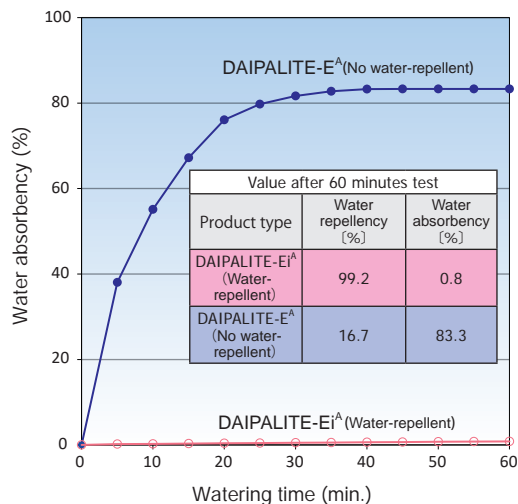

$$\text{Water absorptency} [\%] = (M_1 - M_0) / (V \times \rho_w) \times 100 [\%]$$

$M_0$  : Mass of test piece before test [g]


$M_1$  : Mass of test piece after test [g]

$V$  : Volume of specimen [cm<sup>3</sup>]

$\rho_w$  : Water density 1 [g/cm<sup>3</sup>]

## Stress corrosion cracking inhibition (ASTM C795)

These calcium silicate materials have performance to satisfy ASTM standards as a thermal insulation material in contact with austenitic stainless steel.

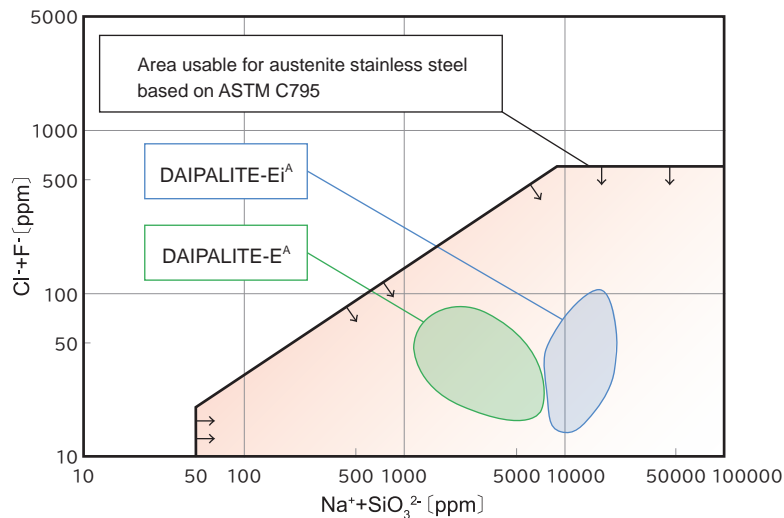

## Standard dimensions [mm]

|            | Internal Diameter | Thickness      | Width                  | Length |
|------------|-------------------|----------------|------------------------|--------|
| Pipe cover | 22 ~ 610          | 25 30<br>40 50 | —                      | 914    |
| Board      | —                 | 65 75          | 303 × 914<br>150 × 914 |        |

## List of ASTM C533 test results

| Property   | Test Methods   | ASTM C533 Requirement  | Test Results |
|--|--|--|--------------|
| Density (Dry) Average*                                     | ASTM C302  | ≤ 240 kg/m <sup>3</sup>  | Pass         |
| Flexural Strength*   | ASTM C203  | ≥ 344 kPa (50 psi)   | Pass         |
| Compressive Strength*                                      | ASTM C165  | ≥ 688 kPa (100 psi)  | Pass         |
| Abrasion Resistance Weight Loss by Tumbling*               | ASTM C421  | After the first 10 min <20%, After the second 10min <40%   | Pass         |
| Linear Shrinkage after Heat Soaking*                       | ASTM C356  | Less than 2% after 24hr, Soaking period at 650°C   | Pass         |
| Hot Surface Performance of High Temperature*               | ASTM C411  | Warpage ≤ 6mm<br>Cracking : no cracks completely through the insulation thickness.<br>Surface cracks on hot face are acceptable  | Pass         |
| Surface Burning Characteristics*                           | ASTM E84   | Flame spread - 0, Smoke Developed-0  | Pass         |
| Apparent Thermal Conductivity*                             | ASTM C177/GHP<br>ASTM C518/HFM<br>ASTM C335/Pipe cover<br>ASTM C1045 | Temp. [°C] 38 93 149 204 260 316 371   | Pass         |
|  |  | λ W/(m·K) ≤ .059 ≤ .065 ≤ .072 ≤ .079 ≤ .087 ≤ .095 ≤ .102   | Pass         |
| Stress Corrosion Performance* (Austenitic Stainless Steel) | ASTM C795<br>ASTM C692<br>ASTM C871                                  | ① Na <sup>+</sup> + SiO <sub>3</sub> <sup>2-</sup> ions : ≥ 50ppm<br>② Acceptable range of Cl <sup>-</sup> + F <sup>-</sup> and Na <sup>+</sup> + SiO <sub>3</sub> <sup>2-</sup><br>③ pH ≤ 12.5 (at 25°C)<br>④ The stress corrosion test (ASTM C692) must be passed. | Pass         |
| Moisture Content*  | ASTM C1616   | ≤ 20%  | Pass         |
| Combustibility*  | ASTM E136  | Non-Combustible  | Pass         |
| Corrosion**  | ASTM C1617   | Mass Loss Corrosion Rate (MLCR) ≤ DI<br>(The MLCR of Type 1 materials, when tested with extracted solutions, shall be equal to or less than that determined when tested with DI Water)   | Pass         |

\* Tested product : DAIPALITE-E<sup>A</sup> \*\* Tested product : DAIPALITE-Ei<sup>A</sup> (Water-repellent type)

DAIPALITE-Ei<sup>A</sup> is a water-repellent material but not a waterproof material. Also, there is no guarantee that the metal to be covered will not corrode. With proper construction and maintenance, DAIPALITE-Ei<sup>A</sup>'s water repellency and corrosion inhibition are effective.



## TOKYO OFFICE

Hulic Kiba Building, 3-7-13, Toyo, Koto-ku, Tokyo, 135-0016, Japan

TEL : +81-3-4500-6775 FAX : +81-3-4500-6780

Website <https://www.jic-bestork.co.jp/> Email [daipalite-e@jic-bestork.co.jp](mailto:daipalite-e@jic-bestork.co.jp)

< Notes and caution >

■ The contents of this pamphlet may be changed without prior notice. In addition, reproduction or transmission of any part of the contents without permission is prohibited.

■ Please see our web site for the details.

August 2024 Revised PT9219E-2408-ver3.4.0